

Characterization of Microstructure and Mechanical Properties of CuCr Alloy Produced by Stir Casting

Sami Abualnoun Ajeel, Rabiha S. Yaseen, Asaad Kadhim Eqal
Department of Production Engineering & Metallurgy, University of Technology
asaadka77@gmail.com

Abstract

The relatively low mechanical properties of pure copper at low and high temperature made it very limited applications. The mechanical properties of the copper can be improved by adding a small amount of elements such as Cr. This work consists of four CuCr alloy castings (0.3, 0.8, 1.2 and 1.5%) by using the stir casting method in an argon atmosphere. Then, the heat treatment was done for these alloys which included solution treatment and aging. Heat treatment was treated at 980 ° C for 1 hour, then water-quenching, followed by an aging treatment at 480 ° C for 2.4 and 6 hours. The Optical Microscopy and the Scanning Electron Microscopy (SEM) with (EDS) were used to study the microscopic structure of the produced alloys. The results showed that the mechanical properties of copper increased with increasing chromium content. The microstructure of the castings consist of the dendritic structure, columnar and segregation. It has been also indicated that after heat treatment and aging, the microstructure changed to fine grains and the clusters disappeared. XRD showed a α -Cu phase and a small amount of CrO₂ in microstructures. The highest value of hardness and the ultimate tensile were 101 Hv and 239.12 MPa, respectively. They were achieved at 1.5wt% addition of Cr at 480°C and 4hrs aging.

Keywords: copper based alloy, dendrite, homogenization, heat treatment, Mechanical properties; Microstructure; Phase transitions

Paper History: (Received: 26-6-2018, Accepted: 11-11-2018)

Introduction

Copper-based alloys have many applications in industry such as railway, connectors, contact wires, lead frame, automobile radiators, pipes, valves and heat exchangers[1, 2]. An important property that makes the copper-based alloys meet the industrial demands is the excellent mechanical strength. Copper-chrome alloys are examples of the precipitate hardening strengthening. This is done by precipitate of fine and uniform particle-dispersion in copper matrix[3, 4]. In addition, chrome have low solubility in copper matrix in room temperature. The casting process is the most economical method for obtaining a part of any desired composition, with any size from a few millimeters to large scale even in case of mass production and

complicated parts. Casting processes have become one of the important techniques which are used to produce several types of alloy especially, in the case of mass production and complicated parts [5]. The production of copper chromium alloys with optimum functional properties is difficult and is associated with technological problems. These problems occur during the melting and liquid metal preparation process [6]. However, the affinity of copper to oxygen carries the greatest difficulty where the low activity of copper results in the formation of soluble oxides. But, the presence of chromium forms Cr₂O₃, which is insoluble and difficult to be eliminated from the bath [7, 8, and 9]. The production of Cu-Cr alloys has been the subject of many investigations [10, 11, 12]. For instance, Sayyed Mohammad et al. studied the effect of water-cooled copper mold on the microstructures and hardness for a for 98.88Cu -1.12Cr %wt alloy cast. There is a copper matrix saturated with chromium, spherical precipitates of chromium separated from the liquid phase during cooling before the initiation of solidification, and a eutectic phase in grain boundary areas. The results show that the hardness of samples increases from Hv 113 to Hv 161 after annealing in a salt bath at 450°C for a holding time of 16 h due to coherent precipitates with the diameter of 11 nm are detectable in the samples before and after the age-hardening stage [11]. Similarly, Lijun Peng et al. investigated the phase transformation of a Cu-0.71 wt% Cr alloy during the aging process at 450 °C. The precipitation sequence of Cu-0.71 wt% Cr aged at 450 °C is supersaturated solid solution (fcc Cr-rich phase), fcc Cr phase, order fcc Cr phase and bcc Cr phase. When the specimen is aged aging for 1 for 24 h, both fcc and bcc precipitates exist in the matrix simultaneously. The strengthening effect of Cr-rich phase precipitated in aging at 450°C for 8 h is calculated to be 146 MPa on the basis of the Orowan strengthening mechanism, which is in quite an accordance with the experimental data (144.5 MPa) [12]. Researches of the Cu-Cr alloy have focused on the study conductivity of copper chrome more than mechanical properties. In the present work, the stir casting process and solution heat treatment with the various addition of Cr content are adapted to study the influence on microstructure and mechanical properties that suitable in the mechanical application.

Experimental Procedure

Material

The purity of copper and chromium that used in this study is 99.78% and 99.4% respectively. The particle size of the chromium powder used is about 75 μm . They analyzed by ICP -AES in IBN SINA FACTORY as tabulated in Table 1. The raw materials were sectioned to 20x20x20 mm in order to the melting materials in stir casting is much easier.

Tools and Equipments

In this work, stir casting method is used. It is consist of induction furnace, graphite crucible and drill. Graphite impeller with a speed of 600 RPM is used to mixing metal melt as shown in Figure 1(a, b, d, and e). Cast iron mold is with two holes diameter 10mm and 16 mm is shown in Figure 1(c). Optical Microscope (OM) observation, Vickers microhardness test of the specimens were measured at 300 g of load using a Digital Micro Vickers Hardness Tester TH714 in Production Engineering and Metallurgy Department/ University of Technology. Hardness at three different points per one specimen was measured randomly, and the mean hardness value was calculated. XRD using a Shimadzu 6000 X-ray diffraction target $\text{CuK}\alpha 1$ radiation with 2θ angle was covered from 15 to 120 degree. Scanning electron microscopy (SEM) was used to investigate microstructures. Energy dispersive spectroscopy (EDS) was applied to identify elements and other microstructural features.

Casting and Molding

The melting of material was done in the pouring temperature of 1230 $^{\circ}\text{C}$ [10]. The process started with the preparation of the charge containing required quantities of different elements of Cu and Cr. Stir casting method with argon atmosphere was adopted to producing the experimental samples. Two types of stirring technique were used. These types were mechanical stir and magnetic field that produced from induction furnace. This is used to increase the wettability between Cr particles and melted metal. The casting mold is preheated to (100– 150) $^{\circ}\text{C}$ before pouring to minimize the casting defects such as shrinkage cavities and refines the grain size is obtained [11]. The raw materials was calculated by using the accurate balance as a percentage of weight after and before casting as shown in Table 2. The difference in percent value is due to lose during casting. Fluxes are usually based on borax, providing covering in addition to its ability to dissolve and collect this objectionable oxide shell. It also leads to increase the fluidity of the liquid metal, which allows floating of oxides and other impurities on the surface of copper melt that causes the slags [12] The use of graphite

or charcoal is necessary to avoid gaseous reactions that contained moisture could motivate with sulfur or hydrogen [13]. This alloy near to chrome-copper alloy standard C81500 [14] Infrared thermometer was used to measure the molten metal temperature. Heraeus HANAU furnace in Production Engineering and Metallurgy Department/ University of Technology was used to done the solution treatment and aging with argon atmosphere as shown in Figure 2 (a, b).

Heat Treatment

The heat treatment that used in this work, was solution treatment at 980 $^{\circ}\text{C}$ for 1 hour and then quenched water. Aging at 480 C for at different time (2, 4, and 6) hours were applied. These processes are done for all casts homogenization and enhancement in the microstructure were obtained.

Sample Preparation

The ingots are produced by stir casting methods as shown in Figure 3. The cast dimension was 16 mm diameter and length 120 mm as rods. These casts were cutted to specimens with dimension 5mm length and 16mm diameter. The tensile test samples dimensions were prepared by using turning machine according to ASTM E8M to identify mechanical properties as shown in the Figure 4(a and b). The specimens taken from each alloy was hot mounted and grinding by electric disk rotary device using different grades of emery papers 120,320,500,1000,2000 and 3000. These grinded specimens are polished with cloth diamond lubricant using the polishing device. The specimens after polishing are etched by Keller reagent (5 g FeCl_3 , 95% methanol, 5 mL HCl) in order to reveal the microstructure and microhardness[15].

Results and Discussion

Microstructure of Cu-Cr Alloys

Figures 5(a, b, c, and f) indicate the microstructure features of cast Cu-Cr alloys was studies by the optical micrographs. It showed the microstructure of alloys cast consists of dendrites α solid solution face-center cubic lattice and eutectic of Cr. These phases demonstrate a substantial microstructural difference with increased of Cr additions. The dendritic arm spacing increases with increasing solidification time. The dendrite size became relatively fine when the chromium content increased from 0.3 to 1.5 wt % as shown in Figure 5 (c and d). It is observed during cast solidification the elongated primary grains, α solid solution dendrite and the fine lamellar Cu-Cr $_2$ eutectic as the intermetallic compound in the grain boundaries. These results will enhance the mechanical properties of Cu-Cr alloys.

Solution Treatment and Microhardness of Alloys

The equiaxed grains are clearly observed in all samples due to the reduction in segregation and dendritic. This reduction is obtained by solution treatment at 1 hr and aging at 480 °C, as shown in Figure 6(a,b,c, and f). It is considered an evidence for the formation of coherent precipitates of Cr in the Cu matrix. In addition, the Cr atom has a slower diffusion rate in the Cu lattice at a lower temperature. It has resulted from distortion lattice that caused by coherency between the matrix and coherent precipitated particles. The effect of Cr element on the hardness of the copper alloys and aging time is shown in Figure 6. The best hardness value is observed at the aging time of 4 hrs. it is obvious that the hardness of the samples increases during the Cr content increased. The hardness of the sample in 4 hrs increases from 76 Hv to 101 Hv when the chrome content increase from 0.3 to 1.5 wt %. From Figure 7, the hardness increases rapidly for all samples at the aging time of 4 hours. Then, it decreases with 6 hours of aging time. This is because of the overaging and coarsening.

Figure 8 (a,b and c) shows the SEM images with EDX analysis of Cu–Cr alloy. In this figure, the microstructures of specimens are precipitates of Cr that formed with aging or that contains more dissolved Cr as solid solution in the copper matrix. As expected from EDX analysis of (0.3 and 0.8) % Cr content shows that the matrix is α Cu phase, while the dark region is a Cr-rich phase as the intermetallic compound. These particles formed inside the Cu matrix that grows by effect of aging[11]. The intermetallic phase of the cast is demonstrated using XRD $\text{CuK}\alpha 1$ radiation as shown in Figure 9. The major strong peaks of α Cu are identified. The other phase associated with the presence of α Cu phase is CrCuO_2 phase. The intensity of the lines of the α phase relative to the intensity of the lines of the CrCuO_2 phase will decrease due to change in total composition and decreases the amount of Cu relative to the amount of Cr [18,19].

Tensile Test

Figure 10 represents the stress-strain diagram for all samples that solution treatment at 980 °C for 1h and aging time at 480 °C for 4 hours. It explains a significant increase in ultimate tensile and yield strengths with increase Cr content. In this figure, when the Cr content increased from 0.3 to 1.5 wt% the ultimate tensile and yield strengths change from 175 Mpa to 239.12 Mpa and 38.97 Mpa to 110.32 Mpa respectively. In addition was observed the increase in hardness from 48.67 Hv to 101.3 Hv with an increase in Cr content as shown in Figure (11). The high strength and hardness accompanied by an increase in strain. These are attributed to the formation of nano-scaled Cr precipitates in the Cu matrix during the aging process. This

is because of the extremely low solubility of Cr in Cu at room temperature and the interactions of grain boundary strengthening and strain hardening that occurs during the tensile test [20]. From Figure (11) the decrease in elongation from 50.7% to 28.5 % was observed with an increase in Cr content. This is due to the precipitation hardening that result from low solubility of solute atoms in the Cu matrix. It is important here to mention that avoid coarse precipitation in solidification or fragment and redistributing the alloying contents is a key factor to the improvement of the mechanical properties of the alloy [21].

Conclusions

Stir casting methods through it two type of stirring technique were used. The effect of Cr content and solution treatment on the mechanical properties of the copper alloy was investigated. The result showed that changes in microstructure were noticed. It also indicated that precipitation strengthening occurred owing to the increase in Cr content. Reduction and the change of dendrites microstructure to equiaxed grains that were formed after solution treatment and aging that indication for recrystallization. The Cr content increased hardness values of samples due to the coherent precipitates formed during cooling at room temperature and in aging treatment. It is found that the formed precipitates are very effective at the increase of the hardness of the material.

Acknowledgment:

This work was supported by University of Technology, Production Engineering & Metallurgy Department, which is gratefully acknowledged

References

Paper in a journal:

- [1]. Zhilyaev, A. Morozova, "Wear resistance and electroconductivity in a Cu–0.3Cr–0.5Zr alloy processed by ECAP" *J. Mater Sci*, pp. 31, 2017.
- [2]. Li-Jun Penga, Hao-fengXie, "Effect of Heat Treatment on the Microstructure of Cu-Cr-Zr Alloy", *Key Engineering Materials*, Vol. 727, pp. 1662-9795, 2016.
- [3]. Steven J Zinkle, "Applicability of copper alloys for DEMO high heat flux Components" *Physica Scripta*, Vol.167, pp10, 2016.
- [4]. Dobatkin, "High strength and good electrical conductivity in Cu–Cr alloys processed by severe plastic deformation" *Materials Letters*, Vol.153 pp.5–9, 2015.
- [5]. Smith W. J., "Copper and its Alloys" *Proceeding of an International Conference Organized By the Institute of Metals Held in Amsterdam*, pp. 32, 1970.

- [6]. RZADKOSZ, M. KRANC, "Refining Processes In the Copper Casting Technology" METABK Vol. 54(1), pp. 259-262, 2015.
- [7]. St.Rzadkosza,M. Kranc," Research on Technology of Alloyed Copper Casting" archives of foundry engineering Vol. 14, pp. 79 –84, 2014.
- [8]. Milan. Jovanovic, "Copper Alloys With Improved Properties: Standard Ingot Metallurgy" Vs. Powder Metallurgy, Metal. Mater. Eng. Vol 20 (3), pp. 207-216, 2014.
- [9]. Shangina J. Gubicza E. Dodony,"Improvement of strength and conductivity in Cu-alloys with the application of high pressure torsion and subsequent heat-treatments "J. Mater Sci. Ultra-fine grained Materials, pp.4, 2014.
- [10]. Que, J.H.Lee, H.M.Jung, J.H.Shin, S.Z.Han, K.J.Euh, "Microstructure Evolution in Cu–1.54 Wt% Cr Alloy During Directional Solidification" Journal of Crystal Growth 362, pp. 58-61, 2013.
- [11]. Seyyed Mohammd Hossein Hejazi , "A Cu-Cr alloy with nano and microscale Cr particles produced in a water-cooled copper mold" International Journal of Minerals, Metallurgy and Materials Volume 17, pp. 629, 2010.
- [12]. Sponsored by KBM,"Properties and Applications of copper Chromium (CuCr) Master Alloy from "KBM, pp.7, 2014.
- [13]. Stephen M. Copley "Heat Treating ASM Handbook" Volume 4, ASM Handbook Committee pp 1356, 1991.
- [14]. Sami A. Ajeel, Ahmed N. Ibrahiem, Abdul Salam A. Fadhil, "Study on Improvement of Casting Conditions for Some Aluminum Bronze Alloys" Eng. & Technology, Vol.25, No.6.,pp.2, 2007.
- [15]. Que a,n, J.H.Lee, "Microstructure evolution in Cu–1.54 wt% Cr alloy during directional solidification" Journal of Crystal Growth Vol.362 pp.58–61, 2013.
- [16]. ChengdongXia , Wan Zhang, "High strength and high electrical conductivity Cu–Cr system alloys manufactured by hot rolling–quenching process and thermomechanical treatments" Materials Science and Engineering A, Vol. 538, pp.295– 301, 2012.
- [17]. Stephen M. Copley "copper and copper alloy ASM Handbook" ASM Handbook Committee pp 92, 1991.
- [18]. IBRAHIM SAĞLAM, "Effect of ageing treatment on wear properties and electrical conductivity of Cu–Cr–Zr alloy" Bull. Mater. Sci., Vol. 34, No. 7, pp. 1465–1470, 2011.
- [19]. CULLITY, "Elements of X-Ray Diffraction" Second Edition, Department of Metallurgical Engineering and Materials Science University of Nôtre Dame, pp. 370-400, 1978.
- [20]. Mohammad Baghani, Mahmood Aliofkhaezaei, and Mehdi Askari, "Cu–Zn–Al₂O₃ nanocomposites: study of microstructure, corrosion, and wear" International Journal of Minerals, Metallurgy and Materials Volume 24, Number 4, pp. 462, 2017.
- [21]. Olofinjana , "Properties of rapidly solidified binary copper alloys" Materials Letters 31, pp 87-92, 1997.
- [22]. Zhao Mei,Lin Guobiao, "Analysis of precipitation in a Cu–Cr–Zr alloy" Research & Development Vol.5 No.4.pp.7, 2008.

Table 1: the analytical chemical composition of the pure Cu and Cr powder.

Alloy	Cu	Cr	Ag	Fe	P	Pb
Pure Cu	99.78	-	0.127	0.05	0.046	0.001
Cr powder	-	99.40	-	0.4	-	0.11

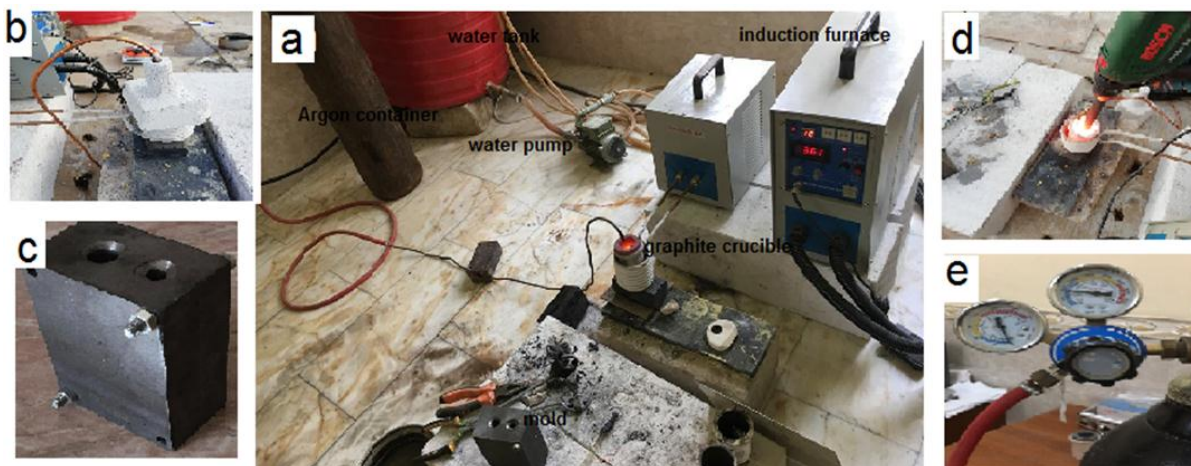


Figure 1: showed (a) Stir casting system, (b) Cup to inert gas, (c) Cast iron mold (d) Stirring with graphite crucible, (e) Argon container.

Table 2: the percent of Cr addition after and before casting of the alloys

Percent of Cr added wt%	Percent analysis after casting wt%
0.6	0.3
1	0.8
1.5	1.3
1.8	1.5



Figure 2: shows (a) solution treatment furnace, (b) Thermometer infrared.



Figure 3: shown the rod casts ingot that produced by stirr casting

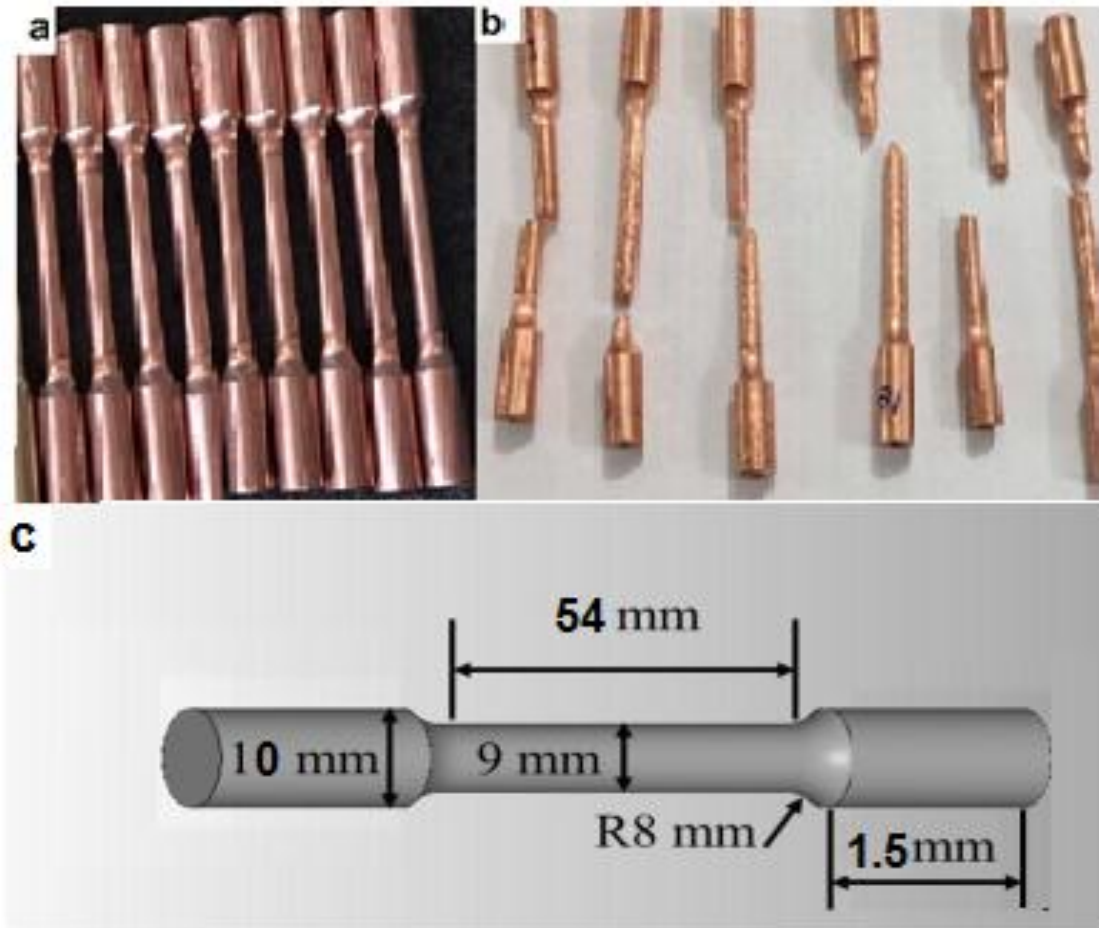


Figure 4: shown tensile test samples (a) before test, (b) after test, (c) standard of tensile test.

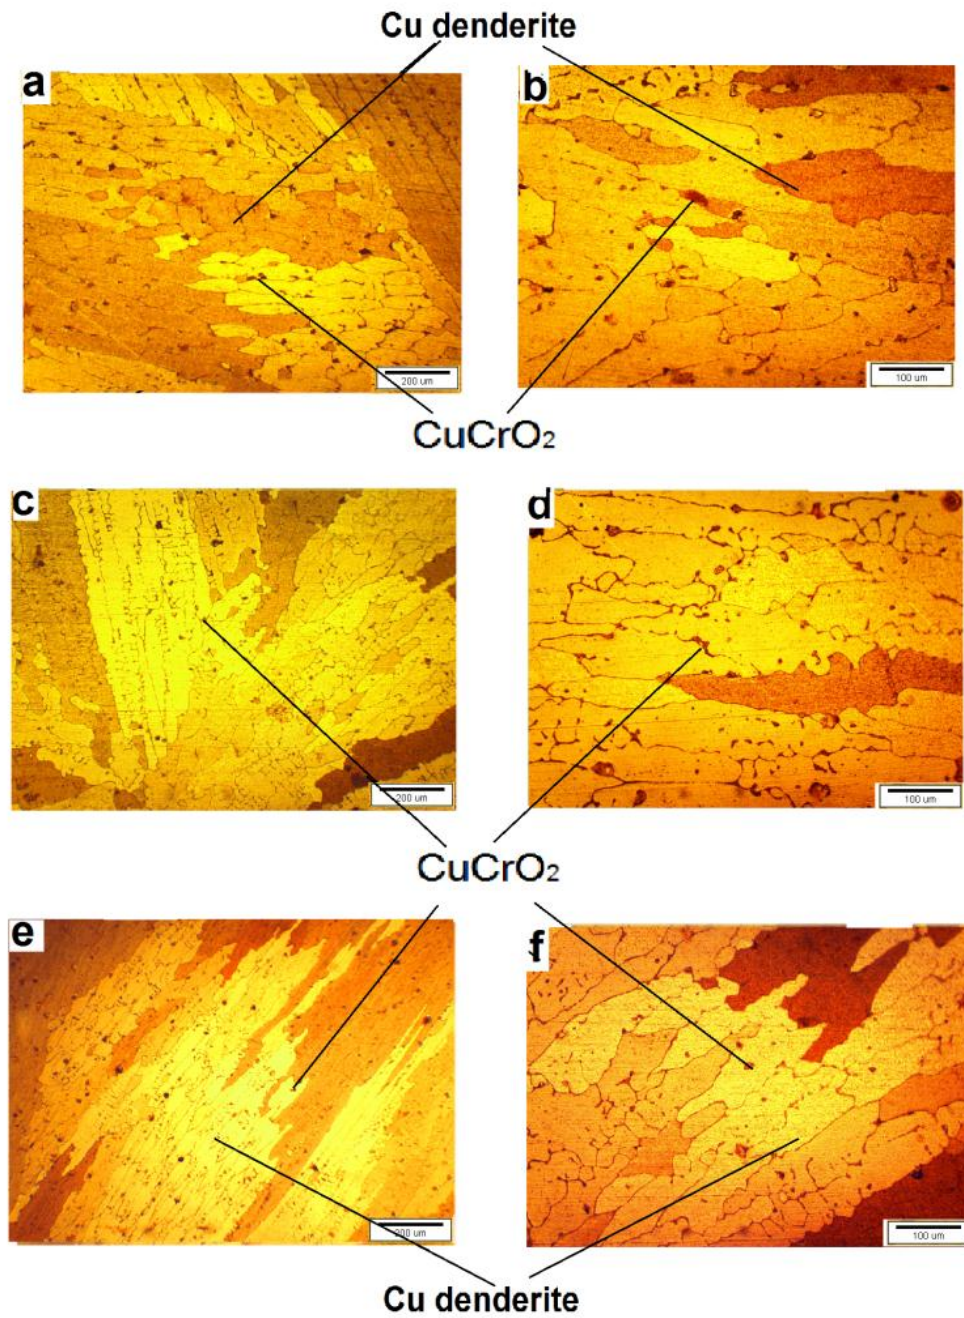


Figure 5: Optical microscope of cast CuCr alloy identified as Cu dendrite of 0.8 Cr wt.% (a,b), 1.3 Cr wt.% (c,d) , and 1.5 Cr wt.% (e,f) at magnification 100X and 200X.

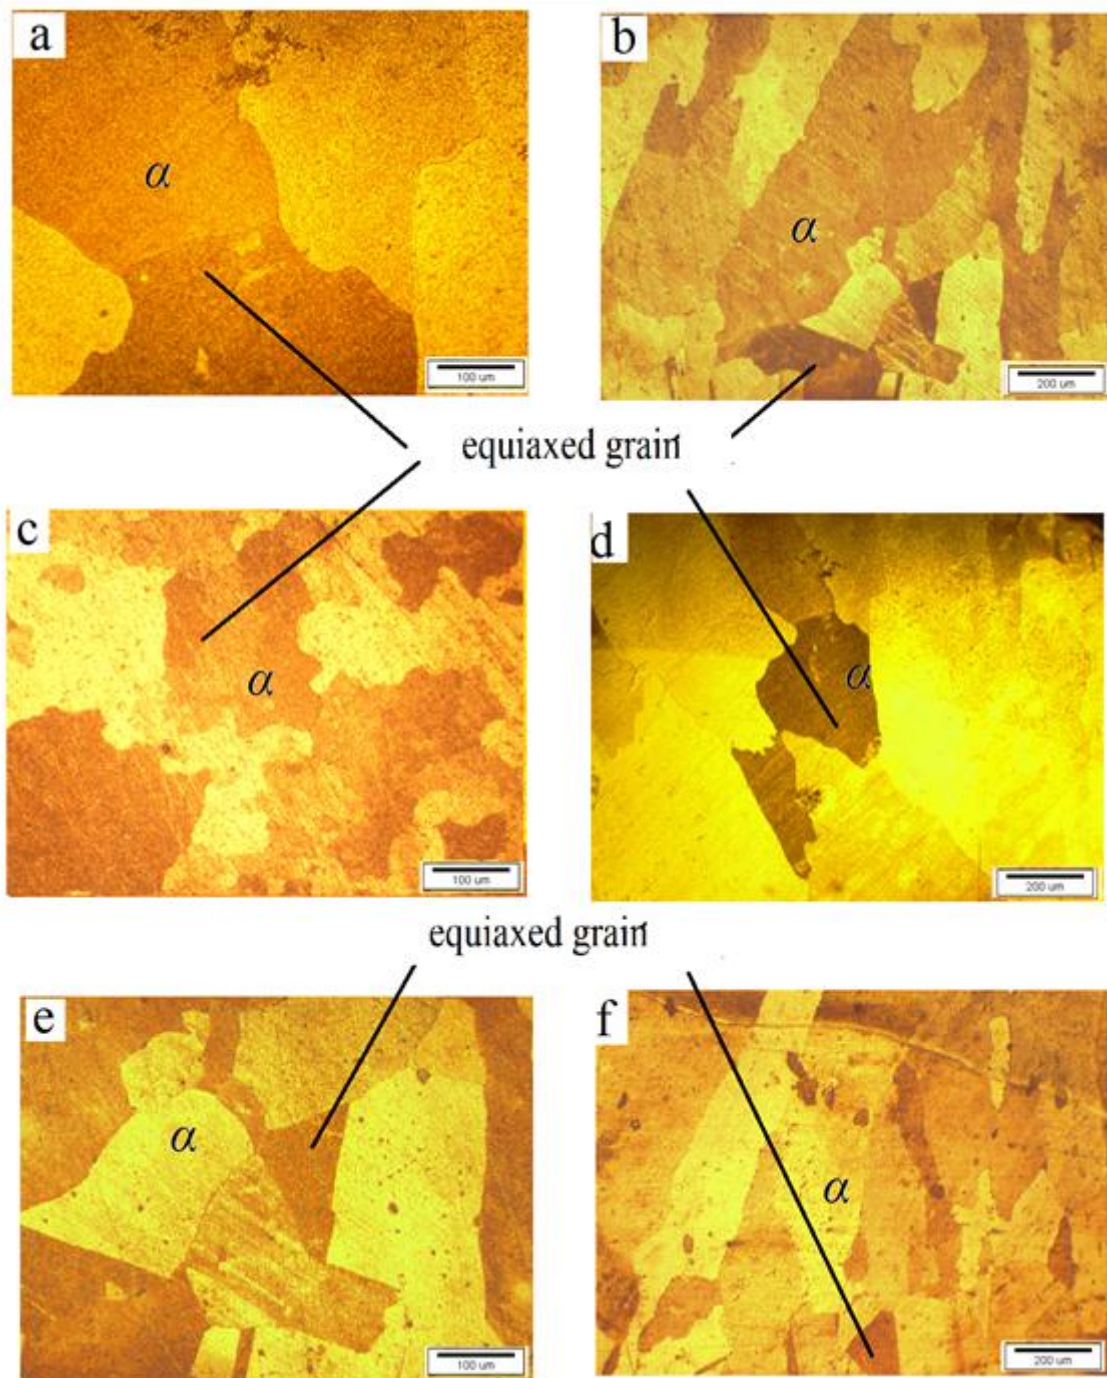


Figure 6: Optical microscope of cast CuCr alloy as equiaxed grains of 0.8 Cr wt.% (a,b), 1.3 Cr wt.% (c,d) , and 1.5 Cr wt.% (e,f) at magnification 100X and 200X

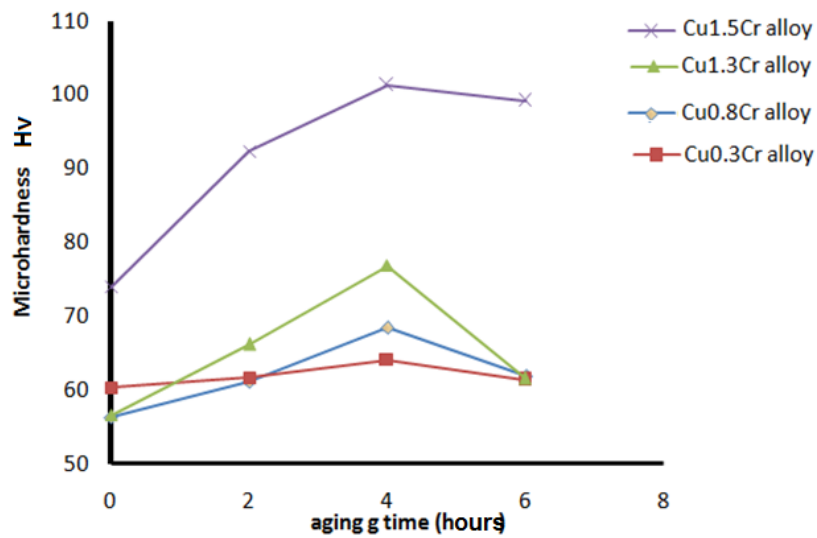


Figure 7: Microhardness measurements of Cu Cr alloy that solution treatment in 980 °C for 1h at different aging time at 480 °C.

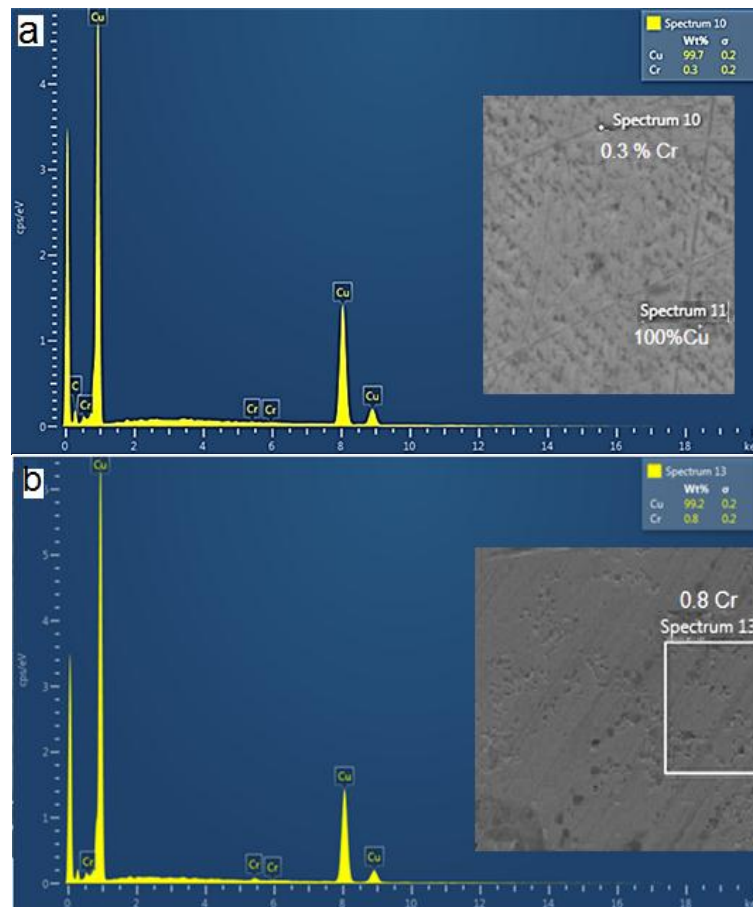


Figure 8: SEM with EDX analysis shown the gray phases are identified as Cu dendrite and the dark region is phase content Cr, Cu-0.3Cr alloy (a), Cu-0.8Cr (b).

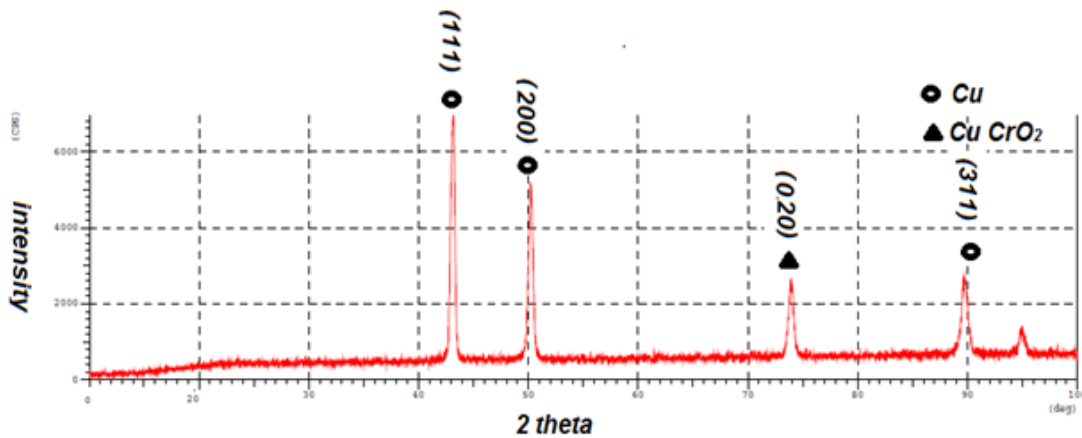


Figure 9: shown XRD using Cu K α radiation Cu peaks of Cu Cr alloy

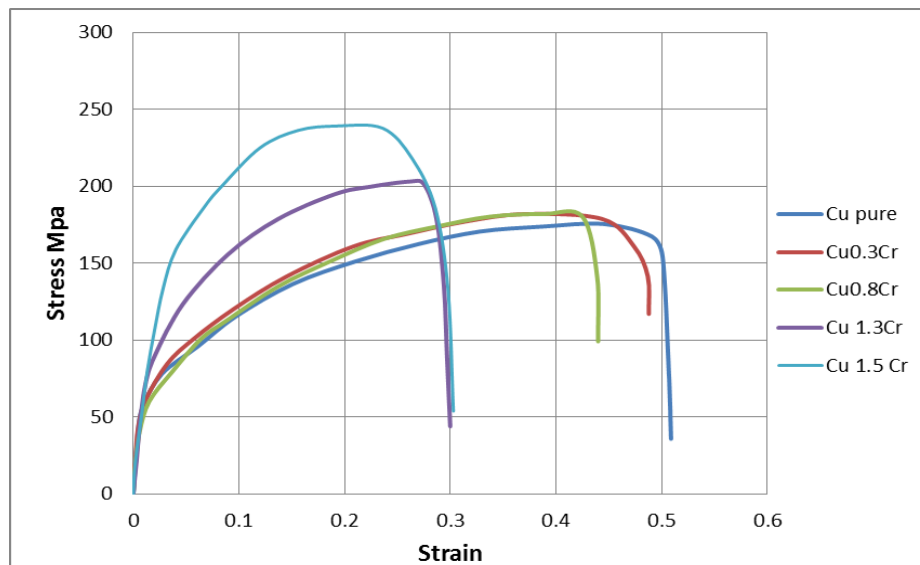


Figure 10: Stress – Strain diagram of Cu Cr alloy that solution treatment in 980 C for 1h and aging at 480 °C for 4h.

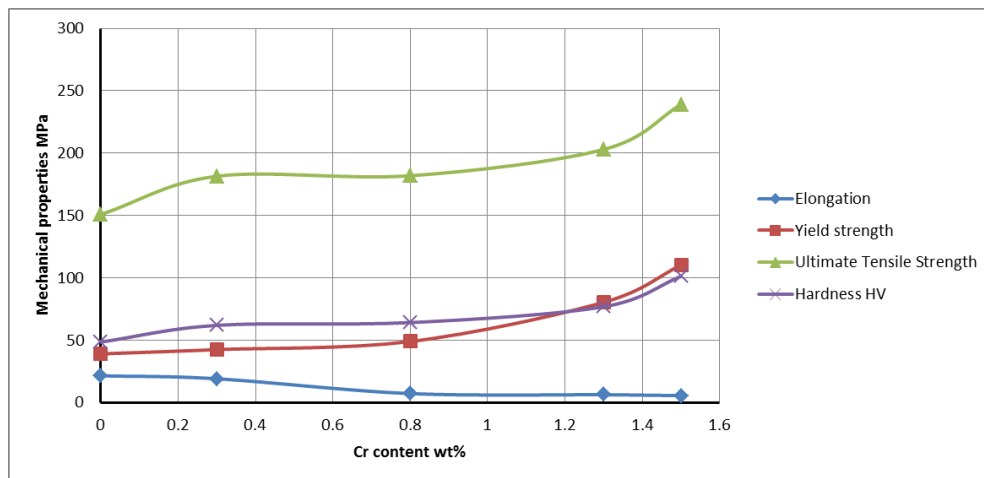


Figure 11: .Effect of Cr additive on the mechanical properties of Cu Cr alloy that solution treatment in 980°C for 1h and aging at 480 °C for 4h

الملاحح المجهرية والخصائص الميكانيكية لسبائك النحاس - كروم المسبوكة بواسطة السباكة بالتدوير

الخلاصة

ان الخصائص الميكانيكية المنخفضة نسبيا للنحاس النقي عند درجة حرارة الواطنة والعالية جعلته محدود التطبيق. ويمكن تحسين الخواص الميكانيكية للنحاس وذلك بإضافة كمية صغيرة من العناصر مثل Cr اليه. يتكون هذا العمل من تحضير أربعة سبائك من مصبوبات CuCr بنسب وزنية (0.3 ، 0.8 ، 1.2 ، و 1.5) % باستخدام طريقة السباكة بالتدوير في جو من الأرجون ، ثم بعد ذلك اجراء المعاملة الحرارية لهذه السبائك والتي تتضمن المعاملة المحلولية والتعتيق. المعالجة الحرارية كانت معاملة محلولية عند 980 درجة مئوية لمدة ساعة واحدة ، ثم تقسية بالماء ، و بعد ذلك يتم إجراء معالجة التعتيق عند 480 درجة مئوية لمدة (2،4) ، و (6) ساعة. تم استخدام المجهر الضوئي المجهر الإلكتروني الماسح (SEM) مع (EDS) الدراسة البنية المجهرية للسبائك المنتجة. أظهرت النتائج أن الخواص الميكانيكية للنحاس زادت بزيادة محتوى الكروم. ان البنية المجهرية للمصبوبات تكونت من بنية الشجرية متكتلة وغير متجانسة. وظهرت النتائج انه بعد اجراء المعاملة الحرارية والتعتيق تغيرت البنية المجهرية الى حبيبات ناعمة متجانسة واختفت التكتلات. وأظهر XRD طور α Cu وكمية صغيرة من طور CrO₂ موجودة في الهياكل المجهرية. وان افضل وان أفضل محتوى من الكروم 1.5 % بالوزن وزمن للتعتيق عند درجة حرارة 480 درجة مئوية وزمن 4 ساعات عطى اعلى صلادة بقيمة 101 Hv واعلى قيمة للشد بقيمة 239.12 Mpa .